



Volume 11, Issue 2, September 27, 2020

Special Edition: Comparison of Test Methods for Human Body Model (HBM) Electrostatic Discharge (ESD)

Damage from ESD is a cause of major costs to the microcircuit industry in terms of time, money, and mission risk. The *EEE Parts Bulletin* has released four special issues on ESD [1]–[4]. The first issue, in 2016, stressed the need to upgrade specifications related to ESD and suggested improved ESD practices wherever parts are manufactured, stored, or prepared for shipment. The second ESD special issue, in 2017, focused on a parts failure investigation that ultimately identified ESD as the most likely cause of the failure. The 2017 special issue also included an important reminder about regular ESD testing. The third issue, in 2018, provided an example demonstrating the importance of maintaining ESD discipline and high-level risk analysis related to ESD. The fourth issue, later in 2018, was a compendium of the previous three special issues and included an overall updated view of the subject matter.

The current special issue focuses on one specific aspect of ESD damage that is caused by the human body during parts handling. The susceptibility of electronic devices to such damage is characterized by the human body model (HBM). For illustration, the magnitude of electrostatic voltage built up on a chip under different handling means and relative humidity (RH) conditions is shown in **Table 1** [1]. A microcircuit device exposed to an ESD event induced by contact with a human body can easily experience an electrostatic voltage attack in the kilovolt range. Thus, a better understanding of HBM ESD events is warranted. In this issue of the *EEE Parts Bulletin*, we report on independent experimental evaluations of two popular HBM-specific test methods: MIL-STD-883 Test Method 3015.7 [5] and JEDEC JS001-2017 [6]. Similar to the latter, the Automotive Electronics Council (AEC) HBM test method is also included for reference. For a fair and straightforward comparison, a chosen microcircuit chip was subjected to HBM zaps under MIL-STD-883 and JEDEC/AEC conditions, respectively.

Table 1. Voltages experienced by electronic devices exposed to various HBM-ESD events [1].

Means of Static Generation	Electrostatic Voltages	
	10–20% RH	65–90% RH
Walking across carpet	35,000	1,500
Walking over vinyl floor	12,000	250
Worker at bench	6,000	100
Vinyl envelopes for work instructions	7,000	600
Common poly bag picked up from bench	20,000	1,200
Work chair padded with polyurethane foam	18,000	1,500

HBM Test Standards

A good overview of HBM test standards was presented in the first *EEE Parts Bulletin* special issue on ESD [1]. In this special issue, we compare and evaluate three popular HBM test standards:

1. MIL-STD-883 Test Method 3015.7 (abbreviated MIL-STD-883) [5]
2. JEDEC JS001-2017 (based on JESD22-A114, abbreviated JEDEC-JS001) [6], [7]
3. AEC-Q200-002 REV-B (abbreviated AEC-Q200) [8]

In the following sections, test methods and classifications for these three test standards are extracted from their respective specification documents. The test methods and classifications are summarized and compared in **Table 5**. There are many similarities between JEDEC-JS001 and AEC-Q200, so the primary focus of the comparison was between MIL-STD-883 and JEDEC-JS001.

MIL-STD-883, Test Method 3015.7

Test Method

MIL-STD-883 stipulates: A sample of devices shall be characterized for the device ESD failure threshold using voltage steps at 500 V, 1 kV, 2 kV, and 4 kV, as a minimum. Each device shall be tested using three positive and three negative pulses with a minimum of 1-second delay separating the pulses.

Classifications

Classifications per MIL-STD-883 are shown in **Table 2**.

Table 2. Device ESD failure threshold classifications for HBM based on MIL-STD-883.

Classification	Voltage Threshold
Class 1	0 to 1,999 volts
Class 2	2,000 to 3,999 volts
Class 3	4,000 volts and above

JEDEC JS001-2017

Test Method

JEDEC-JS001 stipulates: A sample of three devices for each voltage level shall be characterized for the device ESD failure threshold using recommended voltage steps at 50 V, 125 V, 250 V, 500 V, 1 kV, 2 kV, 4 kV, and 8 kV (optional).

Each sample of three devices shall be stressed at one voltage level using one positive and one negative pulse with a minimum of 100 milliseconds between pulses. Longer intervals are permitted and should be used if the devices are expected to be vulnerable to cumulative effects.

Classifications

Classifications per JEDEC-JS001 are shown in **Table 3**.

Table 3. Device ESD failure threshold classifications for HBM based on JEDEC-JS001.

Classification	Voltage Threshold
Class 0Z	0 to 49 volts
Class 0A	50 to 124 volts
Class 0B	125 to 249 volts
Class 1A	250 to 499 volts
Class 1B	500 to 999 volts
Class 1C	1,000 to 1,999 volts
Class 2	2,000 to 3,999 volts
Class 3A	4,000 to 7,999 volts
Class 3B	8,000 volts and above

AEC-Q200-002 REV-B

Test Method

AEC-Q200 stipulates: Each sample group shall be composed of 15 components (five voltage levels with three parts per voltage level) and tested using a direct contact discharge probe at one voltage level, at steps of 500 V, 1 kV, 2 kV, 4 kV, and 8 kV, or using an air discharge probe at 25 kV. Two discharges shall be applied to each pin under test within a sample group and at each stress voltage level, one with a positive polarity and one with a negative polarity.

Classifications

Classifications per AEC-Q200 are shown in **Table 4**.

Table 4. Device ESD failure threshold classifications for HBM based on AEC-Q200.

Classification	Voltage Threshold
Class 1A	0 to 500 volts (DC)
Class 1B	500 to 999 volts (DC)
Class 1C	1,000 to 1,999 volts (DC)
Class 2	2,000 to 3,999 volts (DC)
Class 3	4,000 to 5,999 volts (DC)
Class 4	6,000 to 7,999 volts (DC)
Class 5A	8,000 volts (DC) to 11,999 volts (AD)
Class 5B	12,000 to 15,999 volts (AD)
Class 5C	16,000 to 24,999 volts (AD)
Class 6	25,000 volts (AD) and above

DC = direct contact discharge; AD = air discharge.

The main differences among MIL-STD-883, JEDEC-JS001, and AEC-Q200 test methods and classifications are summarized in **Table 5**.

Table 5. Comparison of MIL-STD-883, JEDEC, and AEC test methods and classifications.

Item	MIL-STD-883	JEDEC-JS001	AEC-Q200
Sample Size	Not specified	Three	Three
First Pulse	500 V	50 V	500 V
Pulses per Zap	3 +ve pulses followed by 3 -ve pulses	1 +ve pulse followed by 1 -ve pulse	1 +ve pulse followed by 1 -ve pulse
Timing Interval between Pulses (min.)	1 second	0.3 second	Not specified
Classifications	Three main groups (1,2,3)	Four main groups (0,1,2,3) and three subgroups (0Z/OA/OB, 1A/1B/1C, 3A/3B)	Six main groups (1,2,3,4,5,6) and two subgroups (1A/1B/1C & 5A/5B/5C)

Experimental Results

The device under test (DUT) selected for this experiment was an octal digital driver fabricated using a rad-hard 1.2- μm complementary metal-oxide-semiconductor (CMOS) technology. This is a common driver chip used in several NASA Jet Propulsion Laboratory (JPL) projects. All of the DUT parts were sourced with the same date/lot code and tested by the same test vendor with the same test procedure and hardware. The HBM test was based on a two-terminal zap apparatus where one terminal was always connected to a virtual switching system (VSS) while the other terminal was applied to the specific test pin of the DUT with other remaining pins floated. Proper HBM-specific waveform calibrations were also performed prior to the start of the experiment.

First HBM Trial: MIL-STD-883 and JEDEC-JS001

A first trial was conducted on this octal driver chip using a common initial 250-V step following test procedures for both MIL-STD-883 and JEDEC-JS001 methods.

Table 6 summarizes the experimental results and observations. The test was conducted under “stop-after-failure” criteria. One can conclude that the majority of the parts failed after the 250-V step per MIL-STD-883 and JEDEC-JS001 classifications. The failure criterion is defined as a $\pm 15\%$ tolerance in measured currents between pre- and post-zapped two-terminal current-voltage (IV) characterization.

Table 6. Summary of first HBM trial (250-V pulse step).

Method	Results
MIL-STD-883	Three parts failed after 250 V
JEDEC	Two parts failed after 250 V One part failed after 500 V

Second Trial: MIL-STD-883

A second experiment was then designed with smaller pulse steps—an initial voltage step of 50 V with 100-V increments in the subsequent zaps: 50 V, 100 V, 200 V.

Table 7 summarizes the results of the second trial-run HBM test based on MIL-STD-883. Two parts (M1 and M2) exhibited fairly gross HBM ESD failures over a majority of the pins. Part M3 showed that it could handle the 200-V (max.) zaps across all its pins. Another common failure signature showed in **Table 6** is that Pins 1–9 of the three parts consistently failed after the HBM zaps.

Table 7. MIL-STD 883–based test results.

SN M1

Pins	50V	100V	200V	300V
1	Failed	NA	NA	NA
2	Failed	NA	NA	NA
3	Failed	NA	NA	NA
4	Failed	NA	NA	NA
5	Failed	NA	NA	NA
6	Failed	NA	NA	NA
7	Failed	NA	NA	NA
8	Failed	NA	NA	NA
9	Pass	NA	NA	NA
11	Pass	NA	NA	NA
12	Pass	NA	NA	NA
13	Pass	NA	NA	NA
14	Failed	NA	NA	NA
15	Pass	NA	NA	NA
16	Failed	NA	NA	NA
17	Failed	NA	NA	NA
18	Pass	NA	NA	NA
19	Pass	NA	NA	NA
20	Failed	NA	NA	NA

SN M2

Pins	50V	100V	200V	300V
1	Failed	NA	NA	NA
2	Pass	NA	NA	NA
3	Failed	NA	NA	NA
4	Failed	NA	NA	NA
5	Failed	NA	NA	NA
6	Failed	NA	NA	NA
7	Failed	NA	NA	NA
8	Failed	NA	NA	NA
9	Failed	NA	NA	NA
11	Pass	NA	NA	NA
12	Failed	NA	NA	NA
13	Pass	NA	NA	NA
14	Failed	NA	NA	NA
15	Pass	NA	NA	NA
16	Failed	NA	NA	NA
17	Pass	NA	NA	NA
18	Pass	NA	NA	NA
19	Pass	NA	NA	NA
20	Failed	NA	NA	NA

SN M3

Pins	50V	100V	200V	300V
1	Pass	Pass	Pass	Failed
2	Pass	Pass	Pass	Pass
3	Pass	Pass	Pass	Failed
4	Pass	Pass	Pass	Failed
5	Pass	Pass	Pass	Failed
6	Pass	Pass	Pass	Failed
7	Pass	Pass	Pass	Failed
8	Pass	Pass	Pass	Failed
9	Pass	Pass	Pass	Failed
11	Pass	Pass	Pass	Pass
12	Pass	Pass	Pass	Pass
13	Pass	Pass	Pass	Pass
14	Pass	Pass	Pass	Pass
15	Pass	Pass	Pass	Pass
16	Pass	Pass	Pass	Pass
17	Pass	Pass	Pass	Pass
18	Pass	Pass	Pass	Pass
19	Pass	Pass	Pass	Pass
20	Pass	Pass	Pass	Pass

Table 8. JEDEC-JC001-based test results.

SN J1

Pins	50V	100V	200V	300V	400V	500V	600V
1	Pass						
2	Pass						
3	Pass	Pass	Pass	Pass	Pass	Pass	Failed
4	Pass	Pass	Pass	Pass	Pass	Pass	Failed
5	Pass	Pass	Pass	Pass	Pass	Pass	Failed
6	Pass	Pass	Pass	Pass	Pass	Pass	Failed
7	Pass	Pass	Pass	Pass	Pass	Pass	Failed
8	Pass	Pass	Pass	Pass	Pass	Pass	Failed
9	Pass	Pass	Pass	Pass	Pass	Pass	Failed
11	Pass						
12	Pass						
13	Pass						
14	Pass						
15	Pass						
16	Pass						
17	Pass						
18	Pass						
19	Pass						
20	Pass						

SN J2

Pins	50V	100V	200V	300V	400V	500V	600V
1	Pass	Pass	Pass	Pass	Pass	Pass	Pass
2	Pass	Pass	Pass	Pass	Pass	Pass	Pass
3	Pass	Pass	Pass	Pass	Pass	Failed	NA
4	Pass	Pass	Pass	Pass	Pass	Pass	Failed
5	Pass	Pass	Pass	Pass	Pass	Pass	Failed
6	Pass	Pass	Pass	Pass	Pass	Pass	Failed
7	Pass	Pass	Pass	Pass	Pass	Failed	NA
8	Pass	Pass	Pass	Pass	Pass	Pass	Failed
9	Pass	Pass	Pass	Pass	Pass	Pass	Failed
11	Pass	Pass	Pass	Pass	Pass	Pass	Pass
12	Pass	Pass	Pass	Pass	Pass	Pass	Pass
13	Pass	Pass	Pass	Pass	Pass	Pass	Pass
14	Pass	Pass	Pass	Pass	Pass	Pass	Failed
15	Pass	Pass	Pass	Pass	Pass	Pass	Pass
16	Pass	Pass	Pass	Pass	Pass	Pass	Failed
17	Pass	Pass	Pass	Pass	Pass	Pass	Failed
18	Pass	Pass	Pass	Pass	Pass	Pass	Pass
19	Pass	Pass	Pass	Pass	Pass	Pass	Pass
20	Pass	Pass	Pass	Pass	Pass	Pass	Pass

SN J3

Pins	50V	100V	200V	300V	400V	500V	600V
1	Pass	Pass	Pass	Pass	Pass	NA	NA
2	Pass	Pass	Pass	Pass	Pass	NA	NA
3	Pass	Failed	NA	NA	NA	NA	NA
4	Pass	Failed	NA	NA	NA	NA	NA
5	Pass	Failed	NA	NA	NA	NA	NA
6	Pass	Failed	NA	NA	NA	NA	NA
7	Pass	Failed	NA	NA	NA	NA	NA
8	Pass	Pass	Pass	Pass	Failed	NA	NA
9	Pass	Pass	Pass	Failed	NA	NA	NA
11	Pass	Pass	Pass	Pass	Pass	NA	NA
12	Pass	Pass	Pass	Pass	Pass	NA	NA
13	Pass	Pass	Pass	Pass	Pass	NA	NA
14	Pass	Pass	Pass	Pass	Pass	NA	NA
15	Pass	Pass	Pass	Pass	Pass	NA	NA
16	Pass	Pass	Pass	Pass	Pass	NA	NA
17	Pass	Pass	Failed	NA	NA	NA	NA
18	Pass	Pass	Pass	Pass	Pass	NA	NA
19	Pass	Pass	Pass	Pass	Pass	NA	NA
20	Pass	Pass	Pass	Pass	Pass	NA	NA

Third Trial: JEDEC-JS001

Table 8 summarizes another group of HBM test results based on JEDEC-JS001. Parts J1 and J2 safely passed the 500-V and 400-V zaps across all pins. Part J3 passed only the 50-V zap. The group of DUTs tested using the JEDEC-JS001 method also showed a common failure signature from Pins 2 to 9.

Discussion

1. ESD-HBM Classifications per Three Standards

Based on MIL-STD-883, JEDEC-JS001, and AEC-Q200 classifications, the highest passing voltage level attained by any one failed part amongst the sample group determines the HBM-ESD classification. Hence, the octal driver chip tested is Class 1 per MIL-STD-3, Class 0 per JEDEC-JS001, and Class 1A per AEC-Q200. Note that such HBM-ESD classification information was not readily provided in vendor datasheets or in the SMD database. Next, based on a comparison of the observed passing voltage level (e.g., 200 V for SN M3 versus 500 V for SN J1), we observe that the MIL-STD-883 test method is apparently more stringent than is the JEDEC-JS001 method. For reference, an HBM-ESD threshold of 2 kV is preferred and typically set as a benchmark in the microcircuit industry—Class 2 based on the three test method classifications. The octal driver chip tested did not meet this threshold.

2. Pulse Steps

Based on results gathered from the first and second trial runs, we see that HBM-ESD failure depends strongly on the pulse step applied in between zaps. Thus, for devices with poor ESD protection, a smaller voltage step will be necessary to differentiate levels of ESD robustness than will be necessary for devices with strong ESD protection.

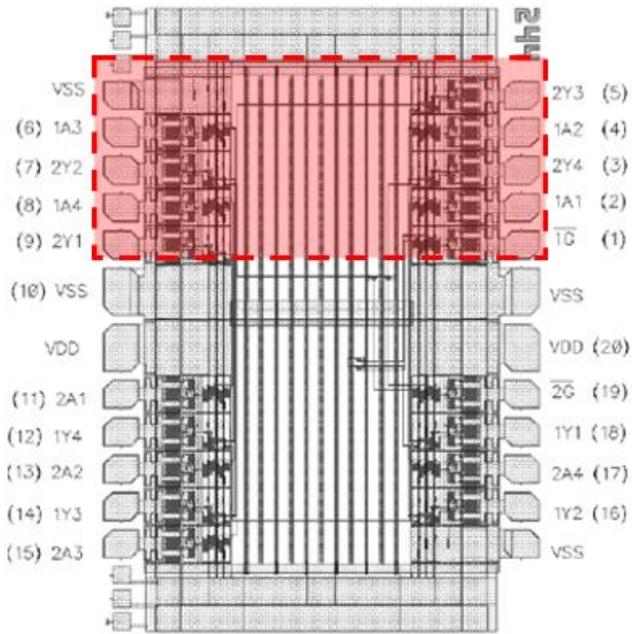


Figure 1. Top-level layout of octal driver chip tested.

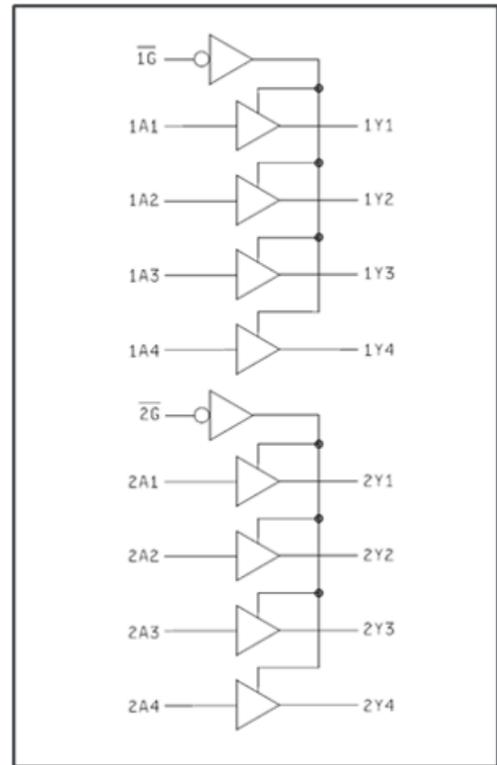


Figure 2. Logic diagram of octal driver chip tested.

3. Weak HBM-ESD Protection

As shown in **Tables 7** and **8**, gross ESD failure occurred across a majority of the input/output pins. Upon further investigation, we found that both test methods identified a common failure signature located in the upper section of the octal driver chips (Pins 2–9). This common failure signature suggests a weak ESD protection network was implemented against HBM-ESD damage for this octal driver chip.

A comparison between the pin definitions and pin failure locations showed no direct correlation between them. These failed pins were independent of Input and output electrical functions. **Figure 1** shows a top-level view of the octal chip’s physical pin layout. The red-highlighted section marks the location of the common failures (Pins 1–9). The corresponding logic diagram of this octal driver is shown in **Figure 2**.

4. ESD Handling

The observed low HBM tolerance as exhibited by this chip suggests that special ESD considerations will be necessary for human handling of this chip. No precaution, warning, or remarks about ESD-sensitive handling was published in the datasheet for the part. In order to handle this chip safely, personnel need proper ESD protections such as grounding strips, anti-ESD suites, and electrostatic ionizers (<50 V) to minimize HBM-ESD damage to the chip during different phases of handling, shipment, and installation.

Conclusions

Based on the experimental results gathered from this work, the MIL-STD-883 and JEDEC-JS001 specifications regarding HBM-ESD are not absolutely equivalent to each other. Different conclusions regarding HBM-ESD robustness and classification will depend on the type of zaps (e.g., pulse step and magnitude). To avoid confusion, it is imperative that microcircuit manufacturers clearly publish such information on their parts’ datasheets. It is also suggested that the more stringent MIL-STD-883 specification be used rather than JEDEC-JS001/AEC-Q200 specifications, despite the expense of longer test times for MIL-STD-883. For any microcircuit device, special attention to ESD handling and mitigation should be triggered whenever basic ESD information is not clearly published in the datasheet.

References

- [1] NASA Electrical, Electronic, and Electromechanical (EEE) Parts Assurance Group (NEPAG), “Special Edition on Electrostatic Discharge (ESD),” *EEE Parts Bulletin*, Volume 8, Issue 1, Revision A, March 14, 2017. [Online]. Available at “Previous Issues” links below.

- [2] NEPAG, "Second Special Edition on Electrostatic Discharge (ESD)," *EEE Parts Bulletin*, Volume 9, Issue 1, June 16, 2017. [Online]. Available at "Previous Issues" links below.
- [3] NEPAG, "Third Special Edition on Electrostatic Discharge (ESD)," *EEE Parts Bulletin*, Volume 10, Issue 1, July 17, 2018. [Online]. Available at "Previous Issues" links below.
- [4] NEPAG, "Compendium Special Edition on Electrostatic Discharge (ESD)," *EEE Parts Bulletin*, Volume 10, Issue 2, April 30, 2019, [Online]. Available at "Previous Issues" links below.
- [5] *Electrostatic Discharge Sensitivity Classification*, MIL-STD-883, Method 3015.7, Defense Logistics Agency, Columbus, Ohio, 22 March 1989. [Online]. Available:
<https://landandmaritimeapps.dla.mil/Programs/MilSpec/ListDocs.aspx?BasicDoc=MIL-STD-883>
- [6] *ESDA/JEDEC Joint Standard for Electrostatic Discharge Sensitivity Testing—Human Body Model (HBM)—Component Level*, ANSI/ESDA/JEDEC JS-001-2017, (This is a revision of JEDEC-JS-001-2014, which supersedes and replaces JESD22-A114F.)
- [7] *Electrostatic Discharge (ESD) Sensitivity Testing Human Body Model (HBM)*. JESD22-A114F, JEDEC Solid State Technology Association, December 2008.
- [8] *Human Body Model Electrostatic Discharge Test*, AEC-Q200-002 REV-B, Automotive Electronics Council, 2010. [Online]. Available:
http://www.aecouncil.com/Documents/AEC_Q200-002B.pdf

Dori Gallagher
dorothy.m.gallagher@jpl.nasa.gov

Brandon Bodkin
brandon.k.bodkin@jpl.nasa.gov

Robert Evans
robert.evans@jpl.nasa.gov

Armian Hanelli
armian.hanelli@jpl.nasa.gov

Shayena Khandker
shayena.j.khandker@jpl.nasa.gov

Erick Kim
erick.n.kim@jpl.nasa.gov

Nazia Ovee
nazia.ovee@jpl.nasa.gov

Claire Marie-Peterson
claire.marie-peterson@jpl.nasa.gov

ATPO
Doug Sheldon
douglas.j.sheldon@jpl.nasa.gov

JPL Electronic Parts
<http://parts.jpl.nasa.gov>

Mohammad M. Mojarradi
mohammad.m.mojarradi@jpl.nasa.gov

Jeremy L. Bonnell
jeremy.l.bonnell@jpl.nasa.gov

PREVIOUS ISSUES

NASA OSMA EEE Parts:
<https://sma.nasa.gov/sma-disciplines/eee-parts>

Other NASA Centers:
<https://nepp.nasa.gov/>

Public Link (Best with Internet Explorer):
<https://trs.jpl.nasa.gov/handle/2014/41402>

Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not constitute or imply its endorsement by the United States Government or the Jet Propulsion Laboratory, California Institute of Technology.

Contacts

Peter Majewicz, NEPP Manager
peter.majewicz@nasa.gov

Jonathan Pellish, NEPP Deputy Manager & NASA-EEE Parts Manager
jonathan.pellish@nasa.gov

Shri Agarwal, NEPAG Coordinator
 818-354-5598
shri.g.agarwal@jpl.nasa.gov

Michael Han
 281-770-7604
michael.han@jpl.nasa.gov